

PLASKOLITE

VIVAK® PETG SHEET

FABRICATION GUIDE



VIVAK sheet

Providing options that work for you

VIVAK sheet offers fabricating, forming, and finishing ease which translates into thinner gauges and higher rates of production, through easy die cutting, punching, and low-temperature forming – on the job site. VIVAK sheet's forgiving nature also means less breakage during production, which can mean higher margins and lower costs.

VIVAK sheet offers deep draws, complex die cuts, and precise molded-in details without sacrificing structural integrity. It can be bonded or fastened with adhesives, tapes, ultrasonic welding or rivets. VIVAK sheet allows you to fabricate large, complex shapes cost effectively compared to competitive thermoplastics. Combine these advantages with a full palette of custom colors and a complete array of finishing options, and you'll see why VIVAK sheet is the answer.

Features and benefits:

- » Complex die cutting
- » Down gauging
- » Riveting
- » Punching
- » Superior impact strength
- » Design flexibility
- » Cold forming

This manual is a general guide for working with PLASKOLITE VIVAK® PETG sheet. Because actual results vary with differences in operating conditions, thickness, color, and composition of the VIVAK sheet, nothing contained herein can be construed as a warranty that PLASKOLITE's VIVAK sheet will perform in accordance with these general guidelines.

Important Notice: Our recommendations, if any, for the use of this product are based on tests believed to be reliable. The greatest care is exercised in the selection of raw materials and in the manufacturing operations. However, since the use of this product is beyond the control of the manufacturer, no guarantee or warranty expressed or implied is made as to such use or effects incidental to such use, handling, or possession of the results to be obtained, whether in accordance with the directions or claimed so to be. The manufacturer expressly disclaims responsibility. Furthermore, nothing contained herein shall be construed as a recommendation to use any product in conflict with existing laws and/or patents covering any material or use. Anyone experiencing problems fabricating VIVAK sheet should refer those questions to the PLASKOLITE Inside Sales Department. This manual does not constitute an offer to sell by the Company. The Company sells ONLY under its current Terms and Conditions of Sale, which appear on its Acknowledgements and invoices. A current copy of the Company's Terms and Conditions of Sale will be supplied upon request. The details provided are believed to be accurate at the time of publication; however, no description is a warranty that the product is suitable for any application. THE COMPANY MAKES NO WARRANTIES, AND UNDERTAKES AND ACCEPTS NO LIABILITIES, EXCEPT ONLY AS SET FORTH IN ITS CURRENT TERMS AND CONDITIONS OF SALE.

CONTENTS

Fabricating

Sawing	3
Routing.....	4
Shearing, blanking, punching.....	4
Laser cutting.....	4
Die cutting.....	4
Drilling	5
Milling	5

Forming

Brake forming and cold bending	6
Strip heating.....	6
Thermoforming	7
Forming equipment	7
Heaters.....	7
Molds	8
Mold design.....	8
Heating cycle	9
Shading or screening	9
Drape and cylindrical forming	10
Free-blown billow forming of dome.....	11
Free-drawn vacuum dome forming.....	11
Registration forming.....	11

Bonding/Fastening

Solvent bonding	12
Transfer tape bonding	12
Welding	12
Mechanical fastening	12

Finishing

Sanding	13
Jointing-planing.....	13
Flame polishing	13
Solvent polishing.....	13
Hot stamping	13
Screen printing.....	13

Performance/Performance Comparison

Physical properties	14
Chemical Resistance	14
Comparison.....	14
Vendors/Contacts.....	15

FABRICATING

Sawing

A circular blade with carbide-tipped teeth utilizing the “triple-chip” tooth design is the preferred method of cutting VIVAK sheet. Table or overhead saws can be used successfully.

Circular saws

Circular saws should be run at relatively high speeds in the range of 8,000-12,000 linear feet per minute. Blades should have 3-5 teeth per inch. As a general rule, thicker gauge sheet requires fewer teeth per inch. A circular saw is preferable to a band saw for straight cuts, because a smoother cut can be achieved. When sawing thin gauge sheet, it is important to have a good supporting edge on the saw table with minimal gap between the saw blade and table edge. When stack cutting, it is a good idea to clamp the top surface to prevent vibration. Be sure tabletops are smooth and free of projections that might scratch or mar the VIVAK.

Band saws

Band saws are useful for trimming formed parts or irregular shapes. Band saws should be run at 2,000 feet per minute and have between 3-15 teeth per inch. Coarser (larger tooth) blades perform better with thicker gauge plastic. Because vibration can induce cracking of VIVAK sheet, proper support of the part to be trimmed is important. If the cut edge is not smooth, cracks will propagate from erose or notched edges.

Note: Always use proper eye protection when sawing

Sawing recommendations

Type of cut	Tool	Blade type	Blade parameters	Blade speed
Straight cut	Circular saw	Triple-chip design	7-1/4" dia., 40 teeth (carbide-tipped cutoff) 7-1/4" dia., 200 teeth (plywood blade)	4,500 rpm
Curved cut	Saber or jigsaw blade	Finish cutting	7 teeth per inch	
Curved cut	Band saw	1/2"	3 teeth per inch	2,000 ft/min
Trimming & deflanging	Router	Carbide-tipped or high-speed steel, double fluted	3/8" dia.	20,000 rpm

Circular saw troubleshooting

Problem:	Melting or gummed edges
Suggested solutions:	<ol style="list-style-type: none"> 1. Increase blade tooth size 2. Reduce saw speed 3. Provide better clamping and/or support for material 4. Use air to cool blade 5. Reduce feed rate 6. Inspect blade for sharpness
Problem:	Chipping
Suggested solutions:	<ol style="list-style-type: none"> 1. Decrease blade tooth size 2. Increase saw speed 3. Increase feed rate 4. Inspect blade for sharpness 5. Check blade and arbor for wobble 6. Check blade fence alignment

Band saw troubleshooting

Problem:	Melting or gummed edges
Suggested solutions:	<ol style="list-style-type: none"> 1. Increase tooth size 2. Reduce saw speed 3. Use air to cool blade 4. Check blade sharpness
Problem:	Chipping
Suggested solutions:	<ol style="list-style-type: none"> 1. Decrease tooth size 2. Slow down stock feed rate 3. Provide better clamping and/or support to eliminate vibration 4. Check blade sharpness

- See page 15 for list of suppliers -

FABRICATING

Routing

Routing produces a smooth edge on VIVAK sheet and can be employed to cut curved or irregular shapes. Routers with a speed of 20,000 to 25,000 rpm are preferred. Use straight fluted carbide-tipped router bits. High-speed steel bits may also be used. Bits should be 3/8" to 1/2" diameter for best results. Portable routers, over-arm routers, or under-the-table routers are all useful. Use a router with at least a 1 h.p. motor.

Special care must be used when routing. Use proper guarding and eye protection. Stock feed rates need to be monitored. Feeding VIVAK sheet, at fast rates can result in shattering. It is important to feed the sheet against the rotation of the router bit and to provide a fence for sizing. Router bits must be kept sharp. Cooling the bit with compressed air during operation will aid chip removal and prolong sharpness.

Shearing, blanking, punching

Other suitable methods for cutting VIVAK sheet include: shearing, blanking, and punching. Shears produce straight-edged cuts, while blanking dies and punches can produce a wide variety of shapes.

VIVAK sheet in gauges up to 0.100" may be sheared using conventional sheet metal power shears. It is important to adjust the blade clearance in relationship to the bed knife. A clearance of 0.001" is desirable to avoid a rough edge cut. Material thicker than 0.100" gauge should be saw cut. Stack shearing of VIVAK sheet is not recommended.

Blanking and punching may be utilized for VIVAK sheet gauges up to 0.100". Other fabrication techniques such as sawing, drilling, and routing should be used for thicker gauges.


Laser cutting

Laser beams can be used to cut VIVAK sheet in thicknesses up to 0.187". Laser power and travel speed must be optimized in order to minimize whitening while cutting VIVAK sheet.

Die cutting

VIVAK sheet in gauges up to 0.100" can be die cut using steel rule or matched metal dies. Steel rule dies are the most common type and double bevel blades provide adequate edges for most applications. If improved edge finish is required, try the flush type of blade. Under normal conditions, 3 point (0.042") thick blades work well. Keep the backup pad in good shape. It is important to have parallel alignment of the die and platen.

Die design

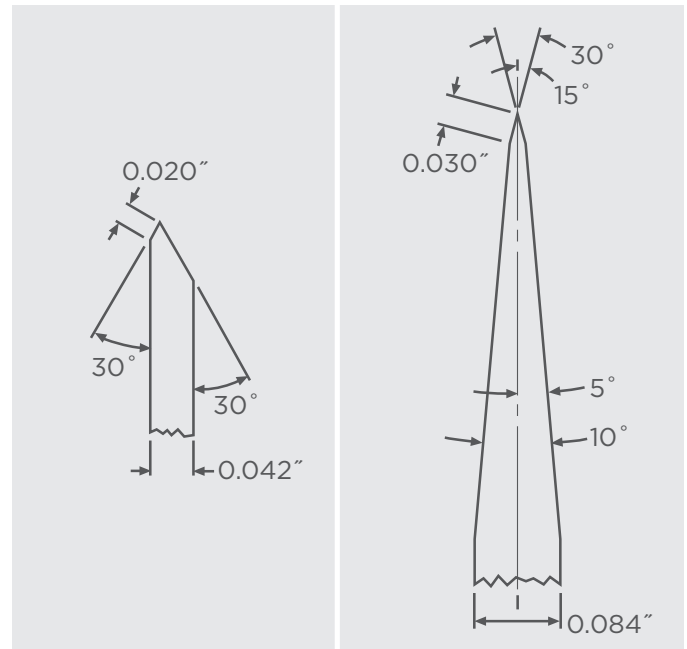


Adequate power in the die press is needed to achieve the desired cut. Calculate the required tonnage by the formula below:

$$F = \frac{PA}{2,000 \text{ lb.}}$$

F = Tonnage of press
P = 9,000 psi
(VIVAK sheet shear strength)
A = Cross-sectional area

Cross-sectional area is determined by the perimeter of the object to be cut times the thickness of blade penetration.

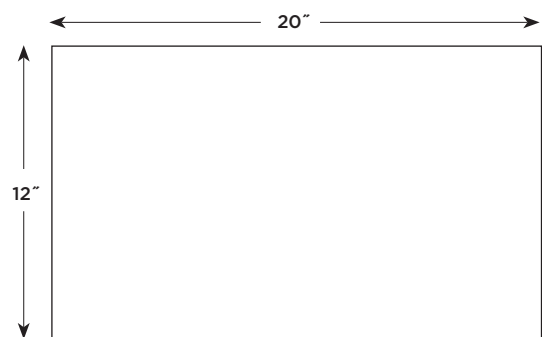

Example:

A 12" x 20" x 0.030" rectangle

$$12 + 12 + 20 + 20 = 64" \times 0.015"$$

*0.015 represents the width of blade at full penetration.

$$64 \times 0.015 = 0.96 = A$$

$$F = \frac{9,000 (0.96)}{2,000} = 4.32 \text{ ton press required force}$$

Drilling

Drills specifically designed for plastics are recommended. Standard twist drills for metal or wood can also be useful.

VIVAK sheet is easily drilled using zero-degree rake angle bits with dubbed off cutting edges. Regulate pressure and speed until a continuous spiraling chip is observed. Back out drill regularly to free chips. This is particularly important when drilling deep holes. Typically, peripheral speeds of twist drills for plastics range from 100 to 200 feet per minute. The rate of drill feed into the VIVAK sheet can vary from 0.010 to 0.025 inch per revolution.

Use air or water as a coolant, if required. Do not use cutting oils. Do not drill and tap or use self-tapping screws. Like most other transparent plastics, VIVAK sheet is a notch-sensitive material and the cutting threads develop stress points that can create stress crazing or cracking.

Be sure drilled holes are smooth with no evidence of cracks or roughness, which can cause weak areas in fastening. Always hold or clamp securely to prevent cracking or slipping and to ensure operator safety.

Milling

VIVAK sheet can be machined with standard high-speed milling cutters for metal, provided the cutters have sharp edges and adequate clearance at the heel. Favorable results can be achieved using a 5/8" diameter bit at 500 rpm with a travel of 5 inches per minute.

- See page 15 for list of suppliers -

FORMING

Brake forming and cold bending

Brake forming and cold bending operations can be used to make simple bends and curved areas with VIVAK sheet.

Brake forming can be done on standard sheet metal brakes. Do not attempt to bend gauges over 0.080", because stress levels are too high and failure can occur.

VIVAK sheet may be cold formed into circular shapes by observing the rule that the radius of curvature must be at least 100 times the material thickness. Example: 0.080" gauge = 8" radius (16" diameter circle).


Strip heating

Because of its low thermoforming temperature, VIVAK sheet is easy to strip heat and line bend.

Using a device similar to the illustration shown, regulate the heat to a temperature that allows VIVAK to reach 280°F. Thicker gauge VIVAK sheet requires a longer period of time to allow heat penetration.

Procedure

- » Remove protective masking from area to be bent
- » Regulate heat source to allow VIVAK sheet to reach 280°F - 320°F
- » Place sheet over heat source at bend area
- » Allow heat to soften material; time depends on gauge, 1/8" normally requires 2 minutes
- » Remove sheet and make desired bend, and place in wood or fabric-covered aluminum fixture
- » Allow bent part to cool in fixture

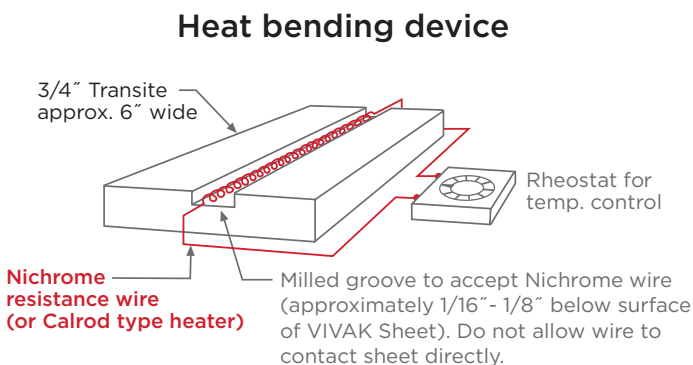

Strip heating troubleshooting

Problem:	Bubbles in bent area
Possible cause:	Too much heat
Suggested solution:	1. Reduce temperature

Problem:	Warpage
Possible cause:	Part too wide for strip heating, heating not uniform
Suggested solutions:	1. Check for drafts 2. Check heat source for uniformity

Possible cause:	Cooling not uniform
Suggested solutions:	1. Check for drafts 2. Cooling fixtures may be removing too much heat in an area

Problem:	Mark off
Possible cause:	Heater is contacting plastic
Suggested solution:	1. Increase gap between heater and sheet

Possible cause:	Transite is too hot
Suggested solution:	1. Increase width of slot in transite

Possible cause:	Masking not removed in wide enough area
Suggested solution:	1. Remove masking further away from heated area

TECH TIPS:

Try to reproduce the suggested steps accurately from part to part.

Avoid drafty rooms which can cause uneven heating and cooling.

Be sure to cover forming fixtures with soft fabric to avoid scratching VIVAK sheet.

Overheating can cause bubbles along bend area.

Bending VIVAK sheet when it is too cold results in a highly-stressed, weakened part.

Thicker gauges (over 0.125") may require heating on both sides by turning the sheet over periodically during the heating cycle. Always bend the sheet with heated side forming the outside radius.

Thermoforming

VIVAK sheet can be thermoformed on standard equipment. The most extensively used processes are vacuum forming, free-blown forming, and line bending.

Forming equipment

The thermoforming machine should be capable of generating and maintaining sufficient vacuum pressure throughout the thermoforming cycle. A minimum of 20 in. Hg. throughout the entire vacuum cycle is required to retain part integrity.

Most commonly used vacuum forming machines with infrared heating elements perform well for VIVAK sheet forming. Rotary and shuttle designs with automatic or semiautomatic controls are most suitable. Key features of this type of equipment include: timer control accuracy, uniform heating sources, and sufficient vacuum power. Single-sided heating has proven effective for VIVAK sheet in gauges up to 0.177". For thicknesses above 0.177", dual-sided heating ovens can be used for faster radiation penetration and quicker cycle times.

Heaters

Infrared cal rod, coiled nichrome, or ceramic heating elements provide the best heating sources. Uniform heating of the sheet is critical.

Typical mold materials thermal conductivity properties

Material	Heat transfer rate factor	K value BTU/HR/SF/F/FT
Aluminum	6190	130
Steel	1238	26
Aluminum filled epoxy	24-47	0.52-0.87
Plaster of paris	8.29	0.17
Epoxy	6.24	0.13
Wood (maple)	4.48	0.09

- See page 15 for list of suppliers -



FORMING

Molds

Although male molds are more suitable for vacuum forming in general, other factors such as part size, finish, and shape must be considered in mold design. Choice of mold materials should be determined by considering the length of the production run. For optimum cost-effectiveness, use the least expensive material that will take the entire run.


It is evident that thermal transfer is much more efficient with aluminum than wood. Wood, however, can be utilized for short-run projects.

VIVAK sheet tends to reproduce mold surface finish quite faithfully, even to the point of replicating wood grain in a smooth wood mold.

Sometimes it is desirable to reduce the polish on a steel or aluminum mold by utilizing a vapor hone or bead blast. This is due to the fact that if the mold surface is too smooth, air entrapment can occur creating "mark off". For best results, use fine hand sanding on the surfaces. Sanding provides tiny channels for air evacuation to prevent air entrapment. This may have to be repeated on long production runs, as the sanded finish smooths out from extended use.

Mold shrinkage

When constructing the mold, mold shrinkage should be a design consideration. Shrinkage for VIVAK sheet is 0.2% - 0.5%. The heating/cooling cycle and the type of vacuum forming equipment will also influence results.

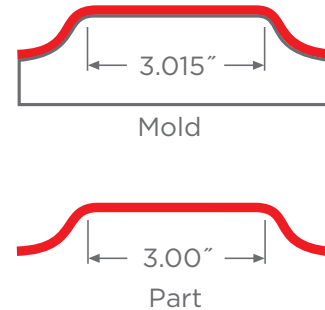

Mold materials and design

VIVAK sheet allows the use of a wide variety of mold materials including: wood, filled and unfilled polyesters, epoxies, and metals.

Molds for vacuum forming need to take only 14 psi, so there is little wear on the tooling with low pressure of the material against the mold surface.

Use standard mold design practices and mold materials.

Mold design

Draft Angles: Minimum 5°-7° or greater for ease of part removal from the mold.

Radii and Fillets: Use generous radii wherever possible for more uniform walls and greater rigidity. On female tooling, use permanent corner fillets.

Vacuum Holes: In order to form the sheet as rapidly as possible, use sufficient holes for fast evacuation of air from between the sheet and the mold. In female molds, use air evacuation holes at all deep draw areas, especially around the mold perimeter where the sheet will be drawn last.

TECH TIPS:


Keep the diameter of the holes small (approximately 1/64" - 1/32" diameter) to avoid marking on the sheet. Long, thin slots may be designed for air evacuation in female tooling.

Use vapor honed or fine sanded finishes.

Avoid sharp corners to minimize stress.

Avoid highly polished surfaces that can cause mark off.

If mold temperature becomes too high during thermoforming runs, VIVAK sheet could stick to the mold. It is recommended that the mold temperature not exceed 140°F.

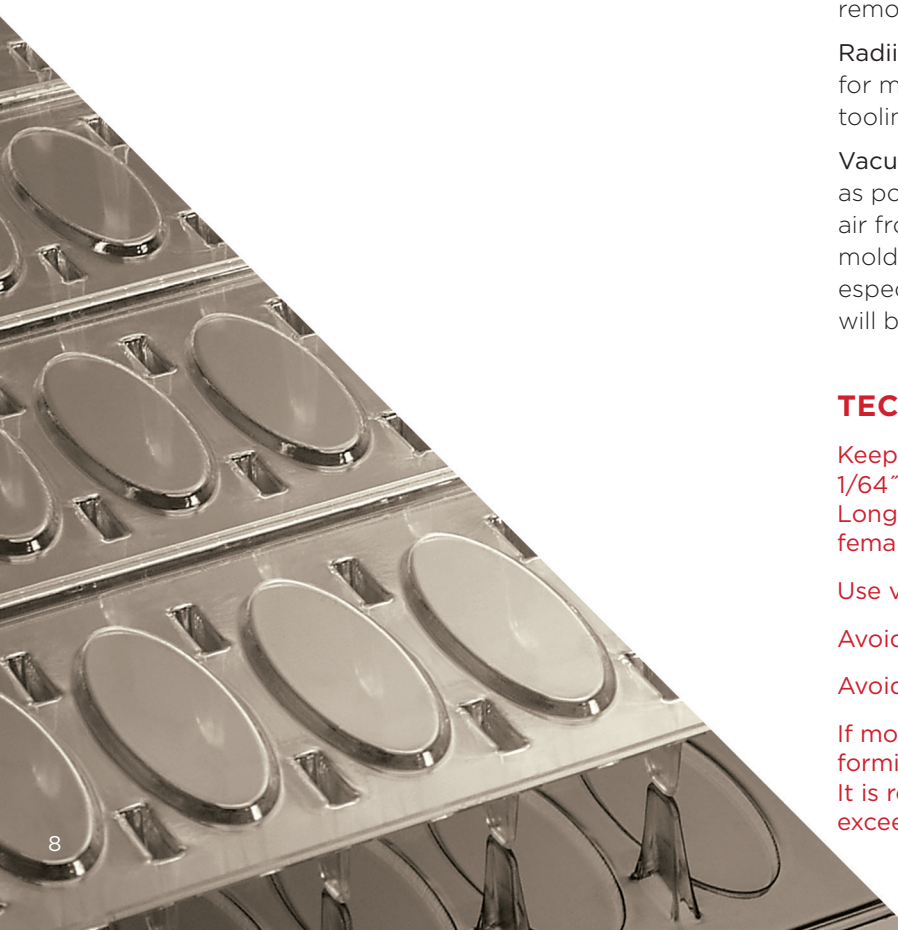

Thermoforming troubleshooting

Problem	Possible cause	Suggested solution
Part weak or crazed	Forming temperature too low	Increase heat setting
Webbing	Uneven Heat	Check for hot spots in heaters
	Mold spacing too close in multiple mold	Spacing between molds should be 2" x height
	Vacuum rate too fast	Restrict vacuum
Part sticks to mold	Mold too hot	Reduce mold temp
	Not enough draft angle	Increase draft
Mark off	Mold finish too smooth	Vapor hone or sand with light finish sand paper
Pinholes on surface	Dust on sheet or mold	Blow off sheet and mold with air
Incomplete part detail	Insufficient vacuum	Check system for vacuum leaks; add vacuum holes
	Sheet too cold	Increase heat setting / setting duration
Bubbles in sheet	Excessive heat	Reduce heat setting / heat duration
Non-uniform sag	Uneven heating	Check heaters
		Screen "hot" areas
Sheet pulls out of clamping frame during forming	Sheet too cold to form	Heat sheet for longer time period

Heating cycle

Heating VIVAK sheet for vacuum forming requires heat penetration to achieve a 280°F to 320°F range. When VIVAK sheet reaches forming temperature, uniform "sag" occurs. The amount of sag depends on the size and thickness of the sheet. A 12" x 12" x 0.060" sheet will sag approximately 1". A 36" x 36" x 0.177" sheet may sag 4"-6" at the center. Once the uniform temperature has been achieved, timers can accurately reproduce the condition, and part-to-part consistency can be maintained.

Procedure

- » Sheet thicknesses up to 0.177" gauge can be heated from one side. Above 0.177" gauge, two-sided heating is normally required to significantly enhance productivity.
- » Heat source is removed and heated sheet is forced over or into mold where vacuum is applied.

FORMING TEMPERATURE GUIDELINES:

Sheet temperature: 280°F - 320°F (typical)

Mold temperature: 130°F - 140°F

Shading or screening

Shading is often used to balance out hot spots in an oven for uniform temperature. Shading may also be used to control the sag of VIVAK sheet during heating.

Procedure

- » Use heavy-duty metal screening to shade the major portion of the clamped sheet, leaving several inches along the edges unshaded to compensate for cooler areas.
- » Screens can be installed permanently or placed loosely above the sheet, depending on how much shading is required.

TECH TIPS:


Throughout the vacuum forming process, it is imperative that dust and dirt be controlled. VIVAK sheet has a static charge that attracts foreign particles which can create surface imperfections. Molds also attract dust particles and should be cleaned to avoid creating surface defects.

Use slow heating. This is particularly important with heavier gauges in order to prevent gradient heating.

Allow heat to reach uniformity at the center of the sheet.

The heating rate may be reduced by lowering the heat intensity or by moving the sheet farther away from the heaters.

FORMING

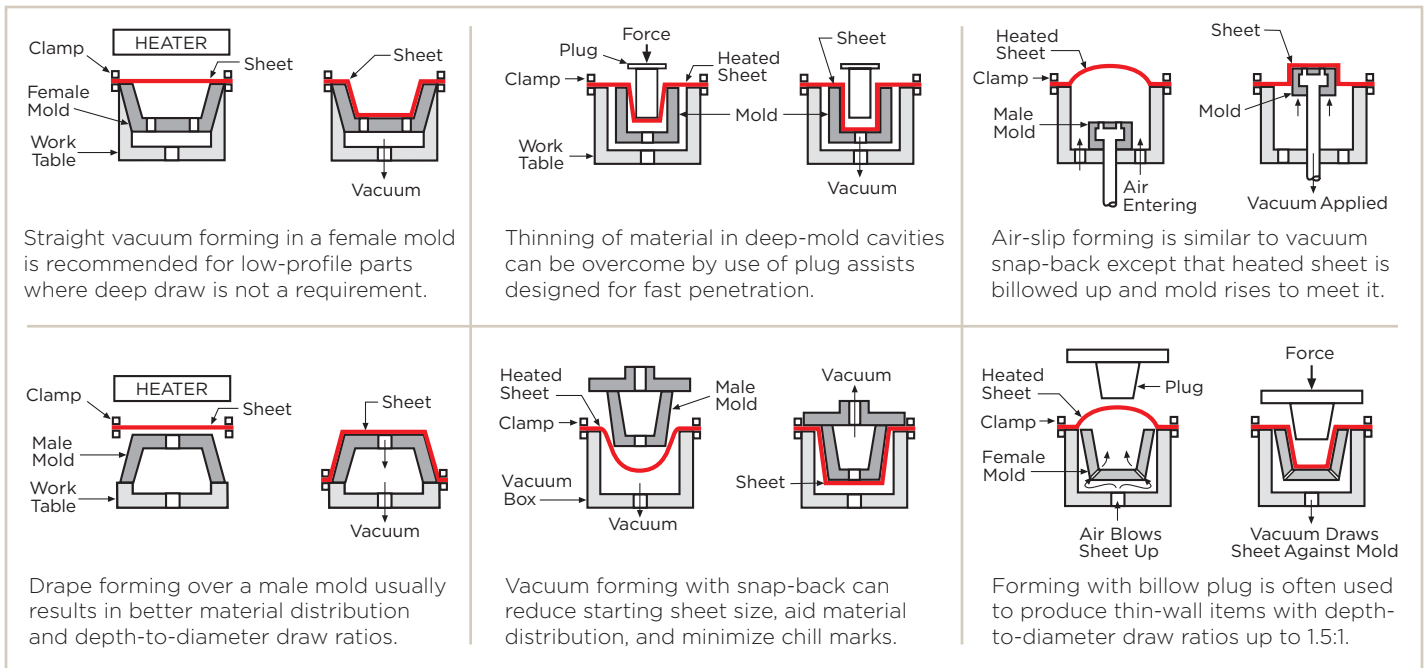



Drape forming

Simple contours can be achieved by drape forming VIVAK sheet.

Procedure

This method can be utilized to manufacture a part requiring a simple radius of curvature. Mold material can be wood, fiberglass, or aluminum covered with felt.

- » Bring to forming temperature of about 280°F - 320°F in the oven
- » Remove parts and immediately place over a male mold covered with felt

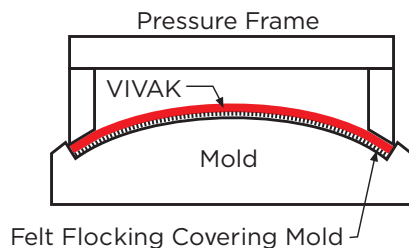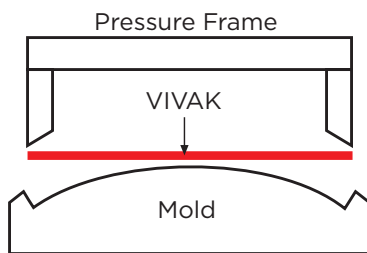


Cylindrical forming

This method is useful for short run projects that are not cost-effective using drape-form molds, or where cold-forming is not applicable (i.e., frameless curved parts).

Procedure

- » Position stops until the desired diameter is achieved
- » Cold form VIVAK sheet into place between stop
- » Heat the VIVAK sheet in curved position for the normal cycle time
- » Allow to cool, then remove from form

Note: Do not overheat. Closely monitor procedure for best results.

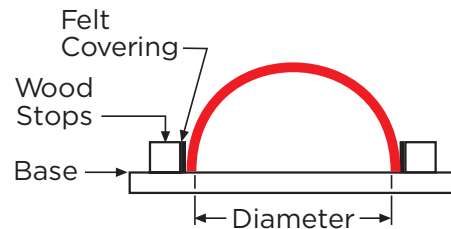


- See page 15 for list of suppliers -

Free-blown billow forming of dome

This process is utilized for forming dome shapes from VIVAK sheet. The procedures and equipment are the same as vacuum forming with the exception of the mold. Billow forming can be done with positive air pressure (free-blown) or negative pressure (vacuum).

Procedure

- » Place VIVAK sheet in clamping frame of thermoforming machine
- » Heat sheet until uniform sag occurs (280°F - 320°F)
- » Remove heat source
- » Lower pressure box to seal air supply pressure
- » Apply air pressure. Initial air pressure is high, and as dome is created, air pressure is reduced.
- » When overall height is achieved, maintain positive air pressure until part cools
- » Be sure air source is properly filtered and uniformly dispersed for even formation of dome
- » Utilize electric eye designs or micro-switches to assure consistent product
- » When dome reaches electric eye, set height. The eye controls air pressure through a solenoid valve to control cooling
- » Remove and trim

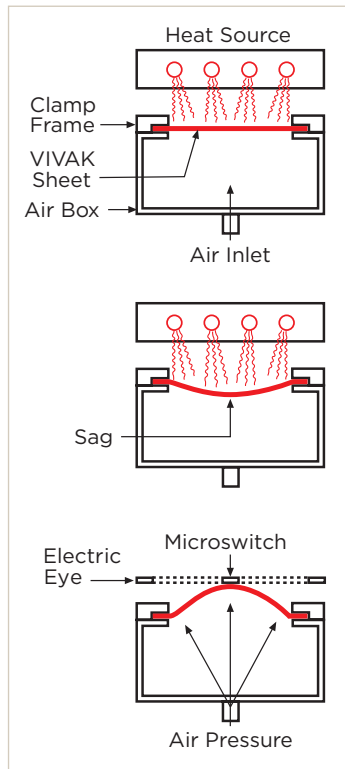


Free-drawn vacuum dome forming

Follow steps involved in vacuum thermoforming. See page 7.

Procedure

- » Place sheet in clamping frame of thermoforming machine
- » Heat sheet until uniform sag occurs (280°F - 320°F)
- » Remove heat source
- » Apply vacuum seal box and apply vacuum pressure
- » Use electric eye or microswitch to assure consistency of depth of dome
- » Retain small amount of vacuum pressure until dome sets up
- » Remove and trim

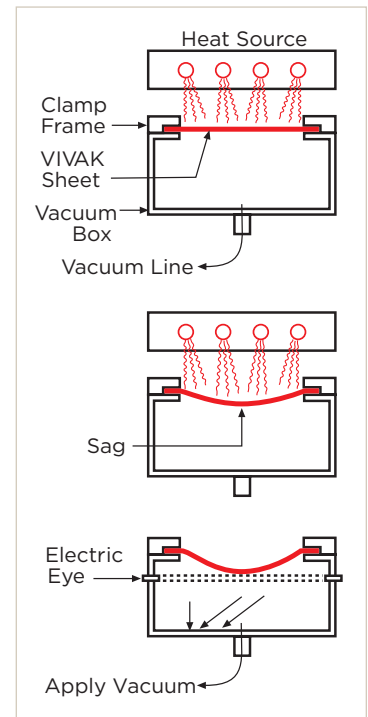

Registration forming

VIVAK sheet is suitable for registration vacuum forming. Because the material is extruded, it is important to orient the sheet so that each part is screened and formed in the same direction each time. Material should be special ordered for this application. Shrink tests indicate VIVAK sheet in free form shrinks about 5% in the direction of extrusion and 1% across the extrusion web.



BONDING / FASTENING

Solvent bonding

Since VIVAK has excellent chemical resistance, it is important to use proper solvent bonding techniques. Solvent bonding will reduce the impact performance of the bonded edge of most materials. When the highest possible impact performance is essential, use flexible adhesive bonding.

Many applications for VIVAK sheet involve fabrication of sheets to construct three-dimensional shapes. The most popular method is to solvent bond. VIVAK solvent bonding can be achieved using methods employed in fabricating other thermoplastics such as acrylic. The two most common methods are needle-type applicator capillary action and edge dipping. Both methods rely on smooth edge preparation, pressure, and curing.

Note: Use extreme caution when working with solvents. Adequate ventilation is essential. Control exposure levels according to OSHA guidelines. Obtain Safety Data Sheets from the solvent manufacturer.

Procedure

- » Smaller items with flat surfaces can be bonded by placing the pieces together and applying the solvent along the edges using a needle applicator or hypodermic syringe. Make sure the solvent flows along the entire joint.
- » For bonding larger items, immerse the surfaces to be joined in the solvent until the material is softened.
- » Apply light pressure and hold until bond is set.
- » Avoid solvent pooling in the joint which can cause joint whitening and stress crazing.

TECH TIPS:

Edges must be clean and free of dirt.

Light sanding of factory polished surfaces will aid in adhesion.

Surfaces should be smooth and properly aligned.

Recommended solvent adhesives include Weld-On #3, Weld-On #4, and MC-Bond.

Bond strength will be enhanced by clamping parts during the adhesive cure.

If joint whitening is observed the following techniques may reduce it:

- Fabricate in a climate-controlled, low humidity area.
- Add 10% glacial acetic acid in the solvent.
- Thicken solvent with resin or plastic shavings.

It is strongly recommended that all products be tested to determine suitability for your specific application.

Transfer tape bonding

Achieving a strong solvent bond using thin-gauge thermoplastics is extremely difficult due to the reduced size of the bond area. However, structural bonding of thin-gauge VIVAK sheet can be accomplished by utilizing acrylic based transfer tapes along with slight design modifications.

Adhesive bonding of VIVAK LAP shear strength¹ psi

	Five minute cure-No gap	One week cure-No gap
Methyl ethyl ketone (MEK)	500	1,500
Cyclohexanone	0	1,100
Tetrahydrofuran (THF)	100	1,500
42% Methyl ethyl ketone (MEK)		
42% Trichloroethylene	400	1,900
16% Methylene chloride		
85% Methylene chloride		
12% Trichloroethylene	200	2,000
3% Methyl ethyl ketone (MEK)		
MC-Bond	NA	NA
"WELD-ON" #3 cement	0	1,800
"WELD-ON" #4 cement	400	2,100

¹ For the purpose of this evaluation, all bonds were 1/2" x 1/4" lap-type bonds between sections of VIVAK tensile bars. Bonds were tested using standard tensile strength test apparatus and a cross-head speed of 2" per minute. All values are 3-test averages to the nearest 100 psi. Values less than 50 psi are listed as "0".

Procedure

- » Bend a small return on the appropriate part to be fastened, approximately the width of the transfer tape
- » Clean tape contact areas with 50/50 isopropyl alcohol-water mixture
- » Apply transfer tape to the return
- » Remove masking and press the part into place

Welding

While mechanical fastening and solvent bonding are the most often recommended methods for joining plastics, another alternative is welding. Ultrasonic spot welding has proven to be an appropriate method. Contact manufacturers of ultrasonic welding equipment for recommendations on section and joint design. Mini extruder welding can also be used to bond VIVAK sheet. Both methods can be used while maintaining FDA approval.

Mechanical fastening

Self-closing rivets and machine screws may be used to join VIVAK sheet parts, if proper consideration is given to the installation. Use oversized holes at least 1/64" larger than the fastener.

A cushion-type washer should be used to avoid localized stress on VIVAK sheet. Use plastic or aluminum fasteners. Mechanical fastening will produce a stronger part than solvent bonded parts and allows for easier disassembly and cleaning.

FINISHING

Sanding

VIVAK sheet can be sanded using both wet and dry techniques. Gumming can result from dry sanding. Wet sanding produces a smooth finish. In both instances, the part will require further finishing in order to restore its high gloss.

VIVAK sheet can also be buffed using a 2-wheel system. The first wheel uses a buffing compound to remove shallow scratches. The second buffing wheel is used for restoring the gloss.

Jointing / Planing

A standard woodworking jointer-planer is an excellent edge finishing machine for VIVAK sheet. Blades must be carbide or high-speed steel. Avoid removal of too much stock on each pass. 1/64" or less stock removal normally yields the cleanest edge. Trying to remove too much material results in a rough edge or shattering of the sheet.

If smoother edges are required, wet sanding with fine grit sandpaper is recommended.

Flame polishing

When flame polishing VIVAK sheet use a standard butane or propane torch. Dress the edges by sanding or jointing to remove the deep tool or saw marks. After torch ignition, be sure to turn down oxygen levels to the lowest possible workable point while still maintaining flame. Pay close attention to controlling the distance between the sheet and the heat source. Without adequate control in these areas, surface whitening or excessive material flow may occur.

Note: As with acrylic, flame polishing VIVAK sheet can cause long-term edge cracking. However, with continued practice and by using proper techniques, excellent results can be achieved in flame polishing VIVAK sheet.

Solvent polishing

In order to improve the look of saw-cut edges, begin by sanding the edges smooth. For smoother, glossy edges, consider solvent polishing with MEK or methylene dichloride. To prevent humidity blush after drying, it may be necessary to add a small amount of a slow-drying component such as diacetone alcohol or glacial acetic acid. Since VIVAK sheet has such good chemical resistance properties, keep in mind that solvent polishing cannot be expected to totally eliminate sand marks from the sheet edge.

Note: Use extreme caution when working with solvents. Adequate ventilation is essential. Control exposure levels according to OSHA guidelines. Obtain Safety Data Sheets for the solvent manufacturer.

Hot stamping

VIVAK sheet is easily decorated by hot stamping. Normal operating conditions are: head (die) temperatures 375°F with 60 psi pressure, with dwell time 2-3 seconds. Contact foil manufacturer for recommended application guidelines.

Screen printing

VIVAK sheet can be printed with conventional printing equipment. Since the ink does not penetrate plastic, special printing inks are necessary. Abrasion can be minimized by applying a light coat of clear lacquer over the printing. Consider each application individually to decide on the best ink for the specific job. Consult with ink manufacturers for best results.

Procedure

- » VIVAK sheet provides an excellent medium for signs, when using standard silk screening equipment with screens of varying mesh (8x to 16x) regulating the amount of ink coverage.
- » Be careful not to exceed the heat distortion temperature of 164°F during the cure process.
- » As with all thermoplastics, it is very important to be sure the sheet is clean and free from dust and dirt prior to screening. Use ionized air to clean dust or pre-rinse with alcohol and a soft, nonabrasive cloth.

TECH TIPS:

After screening, separate sheets on a drying rack until ink is fully cured.

Do not pack sheets for shipment until inks are dry.

VIVAK sheet is not compatible with UV cure screen printing. Ultraviolet curing lamps tend to attack VIVAK sheet, and some loss in physical properties occurs.



PERFORMANCE

VIVAK sheet combines an excellent balance of properties for a wide range of fabricated products

Typical physical properties of VIVAK sheet

Property	Test method	Units	Values
PHYSICAL			
Specific gravity	ASTM D792	-	1.27
Water absorption after 24 hrs.	ASTM D570	%	0.2
Light transmission	ASTM D1003	%	86
Refractive index	ASTM D542	-	1.57
Haze	ASTM D1003	%	1.0
THERMAL			
Deflection temperature @ 264 psi	ASTM D648	°F	157
Deflection temperature @ 66 psi	ASTM D648	°F	164
Coefficient of thermal expansion	ASTM D696	in/in/°F x 10 ⁻⁵	3.8
Glass transition temperature	ASTM D3418	°F	178
Forming temperature	-	°F	280°-320°
MECHANICAL			
Tensile strength	ASTM D638	psi	7,700
Tensile modulus	ASTM D638	psi	320,300
Flexural strength	ASTM D790	psi	11,200
Flexural modulus	ASTM D790	psi	310,000
Izod impact notched at 73°F	ASTM D256	ft-lb/in	1.7
Izod impact notched at 32°F	ASTM D256	ft-lb/in	1.2
Drop dart impact	ASTM D3763	ft-lbs	22
Rockwell hardness	ASTM D785	R Scale	115
FLAMMABILITY			
≥ 0.060"	UL 94	-	HB

VIVAK Chemical Resistance

Resistant to:	Not Resistant to:
Acetic Acid 10%	Acetic Acid (conc.)
Ethylene Glycol (Antifreeze)	Acetone
Brake Fluid, DOT 3	Ammonia
Chromic Acid 20%	Ammonium Chloride
Citric Acid	Ammonium Hydroxide (conc.)
Cottonseed Oil	Benzene
Deionized Water	Carbon Tetrachloride
Detergent, Alconox 0.25%	Chloroform
Di(2-Ethylhexyl) Phthalate	Dimethyl Formamide
Dibutyl Sebacate	Diesel Oil
Diethylene Glycol	Ethyl Acetate
Ethyl Alcohol	Ethylene Chloride
Gasoline (Regular)	Gasohol (Ethanol)
Grease (Automotive)	Gasohol (Methanol)
Hand Cleaner (Jergens SBS 30)	Methyl Ethyl Ketone
Hexane	Methylene Chloride
Hydrochloric Acid 20%	Penetrating Oil (Liquid Wrench #1)
Hydrogen Peroxide 28%	Phenol 5%
Isocetane	Silicone Spray Lube
Isopropyl Alcohol	Silicone Oil
Linseed Oil	Sodium Hydroxide >10%
Kerosene	Sulfuric Acid (conc.)
Methanol	Toluene
Mineral Oil	Tetrahydrofuran
Nitric Acid 10%	
Oleic Acid	
Olive Oil	
Soap Solution	
Sodium Carbonate 20%	
Sodium Chlorate	
Sodium Chloride 10%	
Sodium Hypochlorite 5%	
Spirit, Pure	
Sulfuric Acid 30%	
Transformer Oil	
Transmission Fluid	

Compare VIVAK sheet for interior fabricated and formed applications – It delivers an optimum balance of performance and economy

Performance comparison

Impact strength falling dart @ 73°F ASTM D 5420 @ 0.125"	Acrylic	Polycarbonate	VIVAK sheet
10 in-lbs	Failed	No break	No break
100 in-lbs	Failed	No break	No break
300 in-lbs	Failed	No break	No break
Heat distortion @ 264 psi	203°F	270°F	157°F
@ 66 psi	207°F	280°F	164°F
Gamma stability	Poor	Fair	Excellent
Chemical resistance	Good	Fair	Good

Material availability

Materials	Gauge range	Colors	Patterns	Sizes
VIVAK sheet	0.020" - 0.500"	Standard	Standard	Standard
		Clear	Polished 2 sides	48" x 96"
		Custom		60" x 96"
		Tints		Custom
		Opagues		Available

VENDORS / CONTACTS

Die Cutting Equipment Suppliers:

National Steel Rule Die Co.
3580 Lightner Rd.
Vandalia, OH 45377
Tel: (937) 667-8407
nationaldienyc.com

Atlas Die Inc.
2000 Middlebury Street
Elkhart, IN 46516
Tel: (574) 295-0050
atlasdie.com

Hot Stamping Foil Suppliers:

ITW Foils
5 Malcolm Hoyt Dr.
Newburyport, MA 01950
Tel: (978) 462-7300
foils.itwshinemark.com

Crown Roll Leaf, Inc.
91 Illinois Ave.
Patterson, NJ 07503
Tel: (800) 631-3831
crownrollleaf.com

MC-BOND:

Polysciences, Inc.
400 Valley Rd.
Warrington, PA 18976
Tel: (800) 523-2575
polysciences.com

Paint Suppliers:

Red Spot Paint & Varnish Co.
1107 E. Louisiana St.
Evansville, IN 47711
Tel: (800) 457-3544
(812) 428-9100
redspot.com

AKZO-Nobel
5555 Spalding Drive
Norcross, GA 30092
Tel: (800) 233-2303
akzonobel.com

Saw Blade Suppliers:

Dino Saw, Inc.
340 Power Avenue
Hudson, NY 12534
Tel: (518) 828-9942
dinosaw.com

Forrest Mfg.
457 River Road
Clifton, NJ 07014
Tel: (973) 473-5236
forrestblades.com

Screen Print Suppliers:

Nor-Cote International, Inc.
506 Lafayette Ave.
Crawfordsville, IN 47933
Tel: (800) 488-9180
norcote.com

Kolorcure
1180 Lyon Road
Batavia, IL 60510
Tel: (630) 879-9050
kolorcure.com

Coates Screen Inc.
180 East Union Avenue
East Rutherford, NJ 07073
Tel: (201) 933-6100
coates.de/index.php?lang=en

NazDar
8501 Hedge Lane Terrace
Shawnee, KS 66227
Tel: (800) 767-9942
(913) 422-1888
sourceone.nazdar.com

Strip Heating Suppliers:

FTM Plastic Welding, Inc.
6160 Cobblestone Road
Placerville, CA 95667
Tel: (530) 626-1986
fabricationtoolsandmaterials.com

Craftics, Inc.
2804 Richmond Drive Northeast
Albuquerque, NM 87107
Tel: (866) 296-2130
(505) 338-0005
craftics.net

Transfer Tape Suppliers:

3M/Industrial & Tape
Specialties Division
3M Center, Bldg. 220-7E-01
St. Paul, MN 55144-1000
Tel: (800) 362-3550
3m.com

Saint-Gobain
1 Sealant Park
Granville, NY 12832
Tel: (518) 642-2200
tapesolutions.saint-gobain.com

Ultrasonic Welding Equipment:

Branson Ultrasonics Corp.
41 Eagle Road #1
Danbury, CT 06813
Tel: (203) 796-0400
emerson.com/en-us/automation/branson

WELD-ON® Cements:

IPS® Corporation
455 W. Victoria St.
Compton, CA 90220
Tel: (800) 421-2677
(310) 898-3300
weldon.com



PLASKOLITE

A GLOBAL LEADER IN THE PRODUCTION OF THERMOPLASTIC SHEET

FOUNDED IN 1950

Our Mission: to deliver superior thermoplastic sheet, coatings and polymers to the world, through long-lasting customer relationships and hands-on customer service.

MANUFACTURING LOCATIONS



From our founding, PLASKOLITE strives to treat our employees, our customers, our community and the world, with kindness, dignity and respect. This drives our continuing effort to create sustainable products, in a sustainable manner, for future generations. This on-going commitment is expressed in the

PLASKOLITE Sustainable Ecosystem:

QUICK FACTS

STATUS: Privately held


GLOBAL HEADQUARTERS: Columbus, OH

EMPLOYEES: 1900 Worldwide

MARKETS SERVED: Signage, Lighting, Retail Display, Construction, Transportation, Security, Bath & Spa, Industrial, Architecture, Green Houses

OUR PILLARS OF SUSTAINABILITY

EACH CONTRIBUTES TO MAKING THE WORLD A BETTER PLACE

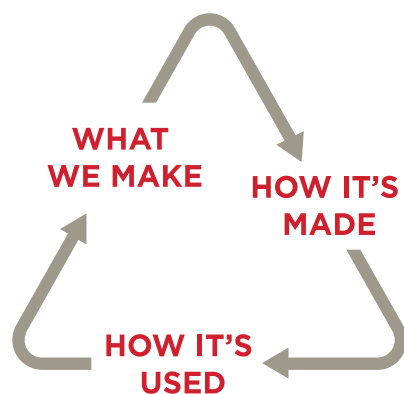

WHAT WE MAKE

Versatile, high-quality, durable thermoplastic materials...not single-use plastics

HOW IT'S MADE

How we make our products reflects our overall philosophy of continuous environmental improvement

HOW IT'S USED

Our thermoplastics play an important role in advancing human well-being, energy conservation and quality of life

These suggestions and data are based on information we believe to be reliable. They are offered in good faith, but without guarantee, as conditions and methods of use are beyond our control. We recommend that the prospective user determines the suitability of our materials and suggestions before adopting them on a commercial scale.

© 2023 PLASKOLITE, LLC 082023
VIVAK® is a registered trademark of PLASKOLITE LLC

PLASKOLITE

CURBELL
PLASTICS

1-888-CURBELL

www.curbellplastics.com

Curbell Plastics is a proud supplier of Plaskolite materials.

400W Nationwide Blvd, Suite 400
Columbus, OH 43215
800.848.9124 • Fax: 877.538.0754
plaskolite@plaskolite.com
www.plaskolite.com

FAB001_VIV